

Substitution for Cu in the electron-doped infinite-layer superconductor $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$, Ni reduces T_c much faster than Zn

C. U. Jung, J. Y. Kim, Min-Seok Park, Heon-Jung Kim, Mun-Seog Kim, and Sung-Ik Lee*

*National Creative Research Initiative Center for Superconductivity and
Department of Physics, Pohang University of Science and Technology, Pohang
790-784, Republic of Korea
(February 1, 2008)*

We report the effect of substitution for Cu on the T_c of the electron-doped infinite-layer superconductors $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}R_x\text{O}_2$ for $R = \text{Zn}$ and Ni. We found that T_c was nearly constant until $x \sim 0.03$ for $R = \text{Zn}$ while the superconductivity was nearly suppressed for $x \sim 0.02$ with $dT_c/dx \geq 20 \text{ K}/\%$ for $R = \text{Ni}$. This behavior is very similar to that of conventional superconductors. These findings are discussed in terms of the superconducting gap symmetry in the cuprate superconductors, including another electron-doped superconductor, $(\text{Nd,Ce})_2\text{CuO}_{4-y}$.

I. INTRODUCTION

Impurity substitution at the Cu site in high- T_c cuprates [1,2] has been considered to be a test probe for the mechanism of high-temperature superconductivity and the symmetry of the superconducting order parameter [3-33]. It has also shed light on the recent striking issue of a normal-state pseudo-gap. [3-5] The most important observation was that the non-magnetic Zn ion suppressed T_c somewhat more than magnetic ions such as Ni for all kinds of hole-doped cuprates such as $(\text{La,Sr})_2\text{CuO}_4$, [3,6-8] $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, [3,6,9-13] $\text{YBa}_2\text{Cu}_4\text{O}_8$, [14,15] and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ [4,5]. The T_c reduction rate for Zn substitution was $dT_c/dx \sim 10 \text{ K}/\%$ and was higher for underdoped compounds than optimally or overdoped ones. This behavior of T_c is strongly contrasted with that of conventional superconductors, where the reduction of T_c is stronger for magnetic ion impurities, but nearly absent for nonmagnetic ion impurities. This difference led to the theoretical formulation of an unconventional pairing mechanism and a symmetry of the order parameter for high-temperature superconductor [16-27].

Substitution at the Cu site in ordinary high- T_c cuprates with a charge reservoir block is generally not immune to structural distortion and/or charge carrier transfer between the charge reservoir block and the conducting CuO_2 planes, which could affect T_c dramatically. Especially, one must be very cautious about the oxygen content when comparing the amounts of T_c reduction directly. Another complexity is due to the existence of several substitutable sites inside a unit-cell.

Electron-doped infinite-layer superconductors $(\text{Sr}_{1-x}^{+2}\text{Ln}_x^{+3})\text{CuO}_2$ ($\text{Ln} = \text{La, Sm, Nd, Gd, etc.}$) [34,35] have several incomparable merits for studying the effect of substitution for Cu on T_c . Without a charge reservoir block, it has only the back-bone structure common to all high- T_c cuprates, CuO_2 planes separated only by a

metallic spacer layer. [36] The structure is robust, and oxygen is very stoichiometric and stable: buckling of the CuO_2 plane, O interstitials and O vacancies were reported to be nearly absent. [37] The T_c has been found to be very robust against modifications of the structure and changes in the magnetic moment due to doping various lanthanide ions at the Sr sites. [38] Thus, the substitution for Cu in the infinite-layer superconductors has the least possibility of changing T_c via secondary routes, and observations should reveal a more intrinsic change in the T_c of cuprate superconductors. However, difficulties in synthesizing high-quality sample has prohibited intense work on these infinite-layer superconductors. [39] Moreover, no work on the Cu-substitution effect has been reported.

Recently, we succeeded in synthesizing high-quality $(\text{Sr}_{0.9}\text{La}_{0.1})\text{CuO}_2$. [39] Here, we report the effect of substitution for Cu on the T_c of the electron-doped infinite-layer superconductors $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}R_x\text{O}_2$ where $R = \text{Zn}$ and Ni. We found that T_c was nearly constant until $x \sim 0.03$ for $R = \text{Zn}$ while the superconductivity was nearly suppressed for $x \sim 0.02$ with $dT_c/dx \geq 20 \text{ K}/\%$ for Ni. This feature is similar to those observed in conventional superconductors.

II. EXPERIMENTAL

Starting materials of La_2O_3 , SrCO_3 , CuO , and ZnO (NiO) with a nominal composition were calcined at $920 \sim 945^\circ\text{C}$ for 36 hours with several intermittent grindings. A pelletized precursor sandwiched between two Ti oxygen-getter slabs was put in a Au or Pt capsule. The capsule, together with an insulating wall and a graphite-sleeve heater, was closely packed inside a high-pressure cell made of pyrophyllite. Details of the sintering under high pressure is found elsewhere. [39] The masses of the homogenous samples obtained in one batch were larger

than 200 mg. The low-field magnetization was measured in the zero-field-cooled state by using a SQUID magnetometer (MPMSXL, Quantum Design) at 10 ~ 20 Oe. The powder X-ray diffraction (XRD) was measured using a RIGAKU X-ray diffractometer. Energy dispersive spectroscopy (EDS) using an electron probe microanalyzer and a field emission scanning electron microscope (JSM-6330F, JEOL) were also used.

III. DATA ANALYSIS AND DISCUSSION

Figure 1(a) shows the X-ray powder diffraction patterns of $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}\text{Zn}_x\text{O}_2$, $x = 0, 0.01, 0.03$, and $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}\text{Ni}_x\text{O}_2$, $x = 0.01$ and 0.02 . The intensity of each pattern was normalized to the intensity of the (101) peak and offset vertically for clear comparison. These XRD patterns show that a nearly single phase with an infinite-layer structure was formed. Peaks corresponding to Zn oxide, Ni oxide, and La oxide could not be identified within the resolution. The smaller peaks at $2\theta \sim 33.5^\circ$ and 37.5° were also found to exist for unsubstituted pristine $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ sample with nearly the same diamagnetic signal; thus they do not correspond to Zn oxide or Ni oxide.

The lattice constants are $a = b = 3.928$ (3.950) Å and $c = 3.433$ (3.410) Å for insulating SrCuO_2 (superconducting $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$). [37–39] The expansion of the a -axis lattice constant is known to be due to the transfer of electron carriers to the CuO_2 planes, and the shrinking of the c -axis lattice constant is simply due to the ionic size effect. [34] The lattice constants from the XRD patterns in Fig. 1(a) for $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{0.98}\text{Ni}_{0.02}\text{O}_2$ and $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{0.97}\text{Zn}_{0.03}\text{O}_2$ are $a = b = 3.943$ Å and $c = 3.417$ Å and $a = b = 3.950$ Å and $c = 3.408$ Å, respectively. The error bars are about 0.003 Å.

We also examined whether Zn was uniformly distributed within the samples of $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}\text{Zn}_x\text{O}_2$ with $x = 0.03$. The microscopic composition of the samples was measured over tens of grains, each with a smaller detecting area of $3 \times 3 \mu\text{m}^2$. The average diameter of a grain was about $10 \mu\text{m}$, and the Zn concentration in the grains was $3 \pm 1\%$. The average Zn concentration was also closer to the nominal value. Since the entire heating process was done inside a Au capsule, a net loss of metallic ions is not likely to occur for the high-pressure synthesis technique. For other samples, the resolution of the EDS was rather insufficient to determine the stoichiometry.

We measured the low-field magnetization and calculated the magnetic susceptibility, $4\pi\chi(T)$, to determine the effect of substitution at the Cu site on T_c . Figure 1(b) shows magnetic susceptibility, $4\pi\chi(T)$, curves for the above samples. The data for $x = 0$ were from a previous result. [39] For Ni substitution, both T_c and the superconducting volume fraction drastically decrease,

and superconductivity nearly vanishes for a 2% substitution with an average T_c reduction rate of $dT_c/dx \geq 20$ K/%. This behavior was confirmed for several samples with $x = 0.02$. However, for Zn substitution, the change in T_c was less than about 2 K until $x \sim 0.03$ where the superconducting volume fraction became less than about half that of the pristine sample. For samples with $x \gtrsim 0.03$, growth of single-phase samples was very difficult. Though we did not confirm the uniformness of Ni inside the sample due to the resolution limit of EDS, the result for dT_c/dx should be a lower bound on the real value. The nearly total suppression of superconductivity in $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{0.98}\text{Ni}_{0.02}\text{O}_2$ seems not to result from the lattice effect because the lattice constants remain much closer to those for superconducting $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ than those for insulating SrCuO_2 . This means that the reduction of the electron carrier density in the CuO_2 plane does not play a dominant role in killing the superconductivity.

Figure 2 shows the reduction rate, dT_c/dx , for Cu-site substitution in high- T_c cuprates: $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$, [4,5] $(\text{La,Sr})_2\text{CuO}_4$, [3,6–8] $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, [3,6,9–13] $(\text{Nd,Ce})_2\text{CuO}_4$, [7,25,31] and $(\text{Sr}_{0.9}\text{La}_{0.1})\text{CuO}_2$. The open and the filled symbols represent the cases of Ni and Zn substitution, respectively.

As noted previously, the T_c reduction rate is higher for Zn substitution in 2-dimensional hole-doped cuprate superconductors, which occupies the majority of high- T_c cuprates. However, this trend was first reversed for an electron-doped superconductor such as $(\text{Nd,Ce})_2\text{CuO}_{4-y}$, which is just one step toward a conventional superconductor in terms of charge carrier type. Our finding for $(\text{Sr}_{0.9}\text{La}_{0.1})\text{CuO}_2$ seems to be the next step. Two kinds of representative n-type cuprates show similar behaviors for the substitution effect on T_c , Ni killing the superconductivity faster than Zn. However the difference is that the substitution effect in $(\text{Sr}_{0.9}\text{La}_{0.1})\text{CuO}_2$ is much closer to those in conventional superconductors with respect to the exact value of the T_c reduction rate dT_c/dx .

Impurity substitution effects in hole-doped cuprates and electron-doped cuprates have been discussed in terms of the superconducting gap symmetry, d -wave and s -wave, respectively [16–27]. Phase-sensitive Josephson tunneling or the presence of a half flux quantum at the center of the tricrystal ring [28] could be a direct test of d -wave superconductivity, but would require high-quality thin films, which have not been feasible for infinite-layer superconductors due to difficulties in film growth. In addition, the pairing symmetry of the $(\text{Nd,Ce})_2\text{CuO}_4$ compound remains to be controversial. [29,30]

Many experimental observations indicate that $(\text{Sr}_{0.9}\text{La}_{0.1})\text{CuO}_2$ has properties which are the most similar to those of conventional superconductors. This compound was reported to have more 3-dimensional superconductivity with the c -axis coherence length, even near zero temperature, being larger than the c -axis lat-

tice constant. [40] The undoped antiferromagnetic insulator $\text{Ca}_{0.85}\text{Sr}_{0.15}\text{CuO}_2$ has been reported to have more 3-dimensional magnetic coupling and that material has been reported to have a stronger 3-dimensional character than other parent insulators of cuprate superconductors, such as $\text{YBa}_2\text{Cu}_3\text{O}_6$, La_2CuO_4 , and $\text{Sr}_2\text{CuO}_2\text{Cl}_2$. [41–44] For example, an estimate of the ratio of the out-of-plane to the in-plane coupling constants for $\text{Ca}_{0.85}\text{Sr}_{0.15}\text{CuO}_2$ was two to three orders of magnitude larger than the corresponding values for $\text{YBa}_2\text{Cu}_3\text{O}_6$ and La_2CuO_4 . [41] A very recent observation of scanning tunneling spectra in $(\text{Sr}_{0.9}\text{La}_{0.1})\text{CuO}_2$ support the existence of an s -wave gap with a superconducting gap $\Delta \sim 13$ meV, as well as the absence of pseudogap. [45]

IV. SUMMARY

We found that in electron-doped infinite-layer superconductors $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}\text{R}_x\text{O}_2$, substitution of the nonmagnetic Zn ion in the CuO_2 plane hardly suppress T_c ($dT_c/dx \leq 0.5$ K/% for $x \leq 0.03$) while substitution of the magnetic Ni ion kills the superconductivity at only $x \sim 0.02$ ($dT_c/dx \geq 20$ K/%). This behavior is similar to that observed for conventional superconductors. This behavior is also consistent with many recent observations, such as the existence of s -wave gap, the stronger 3-dimensionality in superconducting and antiferromagnetic properties.

ACKNOWLEDGMENTS

We greatly appreciate valuable discussions with D. Pavuna, K. Maki, Yunkyu Bang, N.-C. Yeh, A. V. Balatsky, and M. Sigrist. For the EPMA and SEM measurements, we are thankful to Mr. Dong Sik Kim at the Department of Materials Science & Engineering at Pohang University of Science and Technology. This work is supported by the Ministry of Science and Technology of Korea through the Creative Research Initiative Program.

* Electronic address: silee@postech.ac.kr

- [1] Y. Maeno, T. Tomita, M. Kyogoku, S. Awaji, Y. Aoki, K. Hoshino, A. Minami, and T. Fujita, *Nature* **328**, 512 (1987).
- [2] G. Xiao, M. Z. Cieplak, D. Musser, A. Gavrin, F. H. Streitz, C. L. Chien, J. J. Rhyne, and J. A. Gotaas, *Nature* **332**, 238 (1988).
- [3] J. L. Tallon, C. Bernhard, G. V. M. Williams, and J. W. Loram, *Phys. Rev. Lett.* **79**, 5294 (1997).
- [4] J. L. Tallon, *Phys. Rev. B* **58**, 5956 (1998).
- [5] B. Chattopadhyay, B. Bandyopadhyay, A. Poddar, P. Mandal, A. N. Das, and B. Ghosh, *Physica C* **331**, 38 (2000).
- [6] B. Nachumi, A. Keren, K. Kojima, M. Larkin, G. M. Luke, J. Merrin, O. Tchernyshov, Y. J. Uemura, N. Ichikawa, M. Goto, and S. Uchida, *Phys. Rev. Lett.* **77**, 5421 (1996).
- [7] J. M. Tarascon, E. Wang, S. Kivelson, B. G. Bagley, G. W. Hull, and R. Ramesh, *Phys. Rev. B* **42**, 218 (1990).
- [8] T. Nakano, N. Momono, T. Matsuzaki, T. Nagata, M. Yokoyama, M. Oda, and M. Ido, *Physica C* **317-318**, 575 (1999).
- [9] Y. Fukuzumi, K. Mizuhashi, K. Takenaka, and S. Uchida, *Phys. Rev. Lett.* **76**, 684 (1996).
- [10] P. Mendels, J. Bobroff, G. Collin, H. Alloul, M. Gabay, J. F. Marucco, N. Blanchard, and B. Grenier, *Europhys. Lett.* **46**, 678 (1999).
- [11] T. R. Chien, Z. Z. Wang, and N. P. Ong, *Phys. Rev. Lett.* **67**, 2088 (1991).
- [12] D. A. Bonn, S. Kamal, Kuan Zhang, Ruixing Liang, D. J. Baar, E. Klein, and W. N. Hardy, *Phys. Rev. B* **50**, 4051 (1994).
- [13] M.-H. Julien, T. Feher, M. Horvati, C. Berthier, O. N. Bakharev, P. Segransan, G. Collin, and J.-F. Marucco, *Phys. Rev. Lett.* **84**, 3422 (2000).
- [14] G. V. M. Williams, J. L. Tallon, and R. Dupree, *Phys. Rev. B* **61**, 4319 (2000).
- [15] Takayuki Miyatake, Koji Yamaguchi, Tsutomu Takata, Naoki Koshizuka, and Shoji Tanaka, *Phys. Rev. B* **44**, 10139 (1991).
- [16] A. A. Abrikosov, *Physica C* **214**, 107 (1993).
- [17] R. J. Radtke, K. Levin, H.-B. Schuttler, and M. R. Norman, *Phys. Rev. B* **48**, 653 (1993).
- [18] D. Pines, *Physica C* **235-240**, 113 (1994).
- [19] L. S. Borkowski and P. J. Hirschfeld, *Phys. Rev. B* **49**, 15 404 (1994).
- [20] J. Giapintzakis, D. M. Ginsberg, M. A. Kirk, and S. Ockers, *Phys. Rev. B* **50**, 15 967 (1994).
- [21] Y. Sun and K. Maki, *Phys. Rev. B* **51**, 6059 (1995).
- [22] R. L. Fehrenbacher, *Phys. Rev. Lett.* **77**, 1849 (1996).
- [23] S. Haas, A. V. Balatsky, M. Sigrist, and T. M. Rice, *Phys. Rev. B* **56**, 5108 (1997).
- [24] G. Haran and A. D. S. Nagi, *Phys. Rev. B* **54**, 15463 (1996).
- [25] M. D'Astuto and M. Acquarone, in *High Temperature Superconductivity; Models and Measurements*, edited by M. Acquarone (World Scientific, Singapore, 1996), p. 343.
- [26] Y. Sun and K. Maki, *Europhys. Lett.* **32**, 353 (1995).
- [27] K. Maki and E. Puchkaryov, *Europhys. Lett.* **42**, 209 (1998).
- [28] J. R. Kirtley, C. C. Tsuei, J. Z. Sun, C. C. Chi, Lock See Yu-Jahnes, A. Gupta, M. Rupp, and M. B. Ketchen, *Nature* **373**, 225 (1995).
- [29] L. Alff, S. Meyer, S. Kleefisch, U. Schoop, A. Marx, H. Sato, M. Naito, and R. Gross, *Phys. Rev. Lett.* **83**, 2644 (1999).
- [30] C. C. Tsuei and J. R. Kirtley, *Phys. Rev. Lett.* **85**, 182 (2000).
- [31] Jun Sugiyama, Shinya Tokuono, Shinichi Koriyama, H. Yamauchi, and Shoji Tanaka, *Phys. Rev. B* **43**, 10489 (1991).

- [32] E. W. Hudson, K. M. Lang, V. Madhavan, S. H. Pan, H. Eisaki, S. Uchida, J. C. Davis, *Nature* **411**, 920 (2001).
- [33] S. H. Pan, E. W. Hudson, K. M. Lang, H. Eisaki, S. Uchida, J. C. Davis, *Nature* **403**, 746 (2001).
- [34] M. G. Smith, A. Manthiran, J. Zhou, J. B. Goodenough, and J. T. Markert, *Nature* **351**, 549 (1991).
- [35] J. T. Markert, K. Mochizuki, and A. V. Eliott, *J. Low Temp. Phys.* **105**, 1367 (1996).
- [36] T. Siegrist, S. M. Zahurak, D. W. Murphy, and R. S. Roth, *Nature* **334**, 231 (1988).
- [37] J. D. Jorgensen, P. G. Radaelli, D. G. Hinks, J. L. Wagner, S. Kikkawa, G. Er, and F. Kanamaru, *Phys. Rev. B* **47**, 14 654 (1993).
- [38] N. Ikeda, Z. Hiroi, M. Azuma, M. Takano, and Y. Bando, *Physica C* **210**, 367 (1993).
- [39] C. U. Jung, *et al.* submitted to *Physica C*.
- [40] Mun-Seog Kim, C. U. Jung, J. Y. Kim, Jae-Hyuk Choi, Sung-Ik Lee, *cond-mat/0102420* (2001).
- [41] A. Lombardi, M. Mali, J. Roos, and D. Brinkmann, *Phys. Rev. B* **54**, 93 (1996).
- [42] D. Vaknin, E. Caignon, P. K. Davies, J. E. Fischer, D. C. Johnston, and D. P. Goshorn, *Phys. Rev. B* **39**, 9122 (1989).
- [43] A. Keren, L. P. Le, G. M. Luke, B. J. Sternlieb, W. D. Wu, Y. J. Uemura, S. Tajima, and S. Uchida, *Phys. Rev. B* **48**, 12 926 (1993).
- [44] R. Pizzi, M. Mali, M. Matsumura, F. Raffa, J. Roos, and D. Brinkmann, *Phys. Rev. B* **56**, 759 (1997).
- [45] C.-T. Chen, P. Seneor, N.-C. Yeh, R. P. Vasquez, C. U. Jung, J. Y. Kim, Min-Seok Park, Heon-Jung Kim, and Sung-Ik Lee, submitted to *Nature*.

FIG. 1. (a) X-ray powder diffraction patterns for $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}\text{Zn}_x\text{O}_2$ ($x = 0, 0.01, 0.03$) and $\text{Sr}_{0.9}\text{La}_{0.1}\text{Cu}_{1-x}\text{Ni}_x\text{O}_2$ ($x = 0.01$ and 0.02). The intensity of each pattern was normalized to the intensity of the (101) peak and offset vertically for clear comparison. (b) Magnetic susceptibility, $4\pi\chi(T)$, curves for the samples.

FIG. 2. T_c reduction rate, dT_c/dx , for Cu-site substitution in high- T_c cuprates; open symbols are for Ni substitution and closed symbols are for Zn substitution. The squares are for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$, the circles for $(\text{La},\text{Sr})_2\text{CuO}_4$, the up-triangles for $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, the down-triangles for $(\text{Nd},\text{Ce})_2\text{CuO}_4$, and the diamonds for $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$. Note that non-magnetic Zn hardly suppresses the T_c of an infinite-layer superconductor.

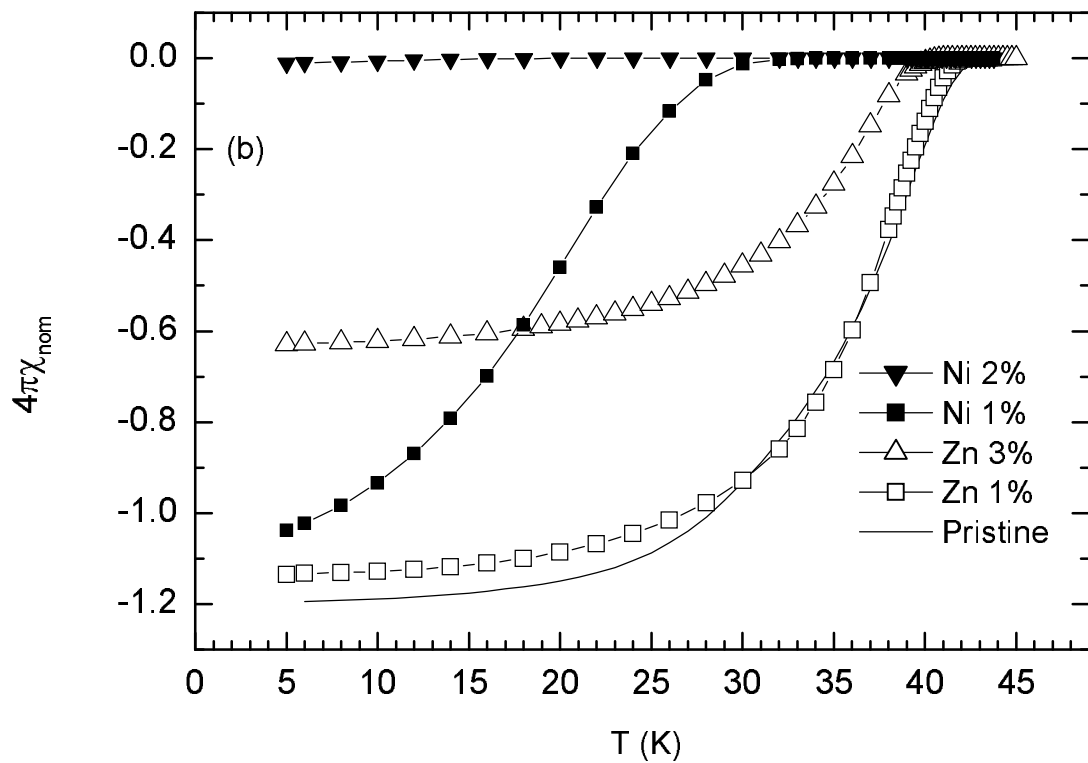
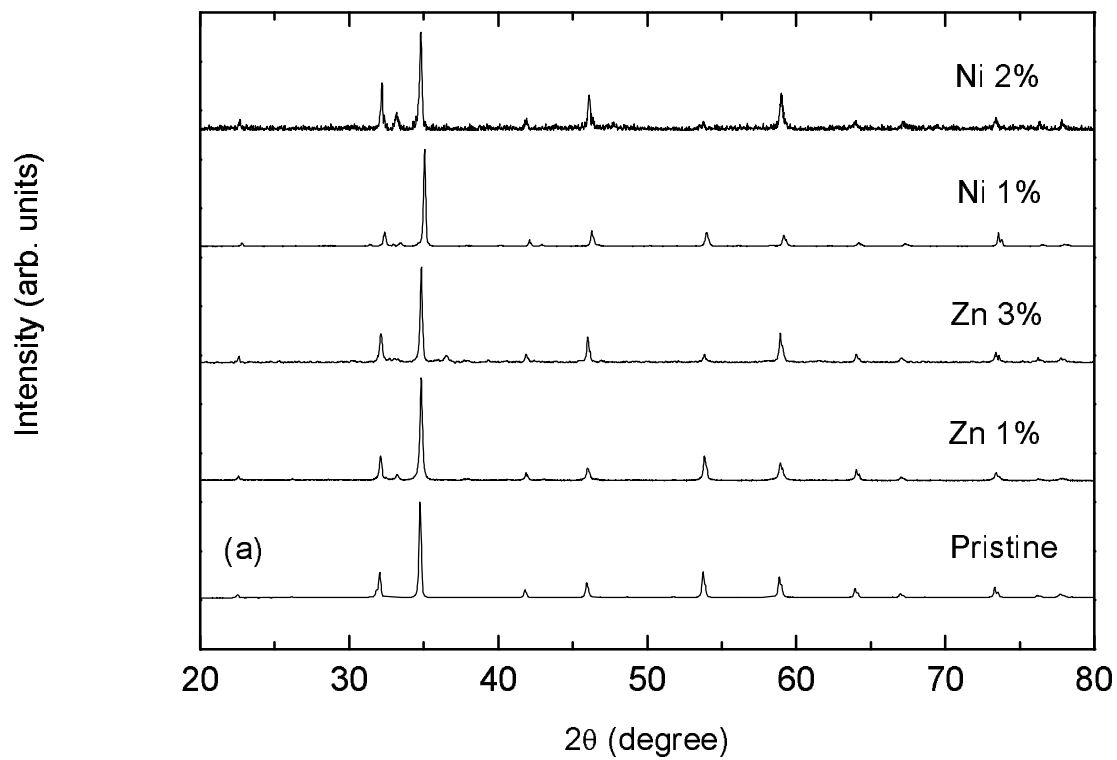


Figure 1, C. U. Jung et al.

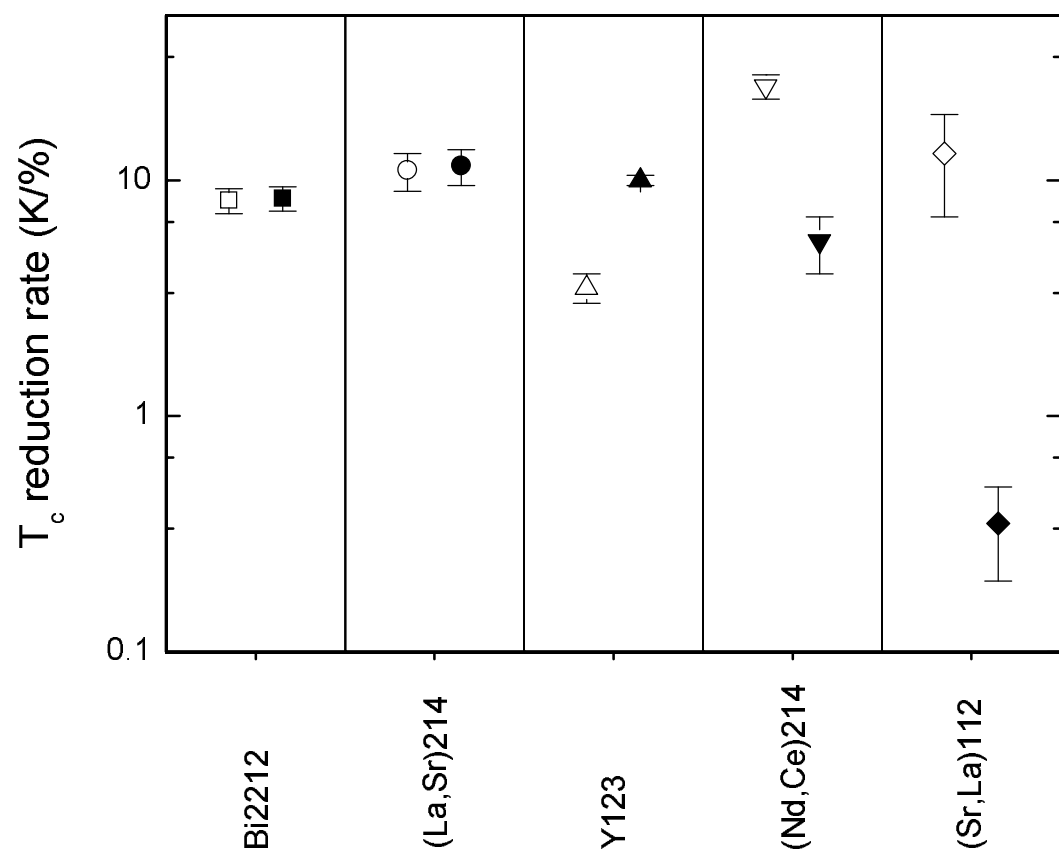


Figure 2, C. U. Jung et al.